AFRL-RX-WP-TP-2012-0385

QUANTIFYING THE EFFECT OF 3D SPATIAL RESOLUTION ON THE ACCURACY OF MICROSTRUCTURAL DISTRIBUTIONS (PREPRINT)

Michael D. Uchic and Michael Groeber
Metals Branch
Structural Materials Division

Megna Shah
UES, Inc.

Gregory Loughnane, Raghavan Srinivasan, and Ramana Grandhi
Wright State University

Matthew Riley
University of Idaho

AUGUST 2012
Interim

STINFO COPY

AIR FORCE RESEARCH LABORATORY
MATERIALS AND MANUFACTURING DIRECTORATE
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7750
AIR FORCE MATERIEL COMMAND
UNITED STATES AIR FORCE

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

1. REPORT DATE *(DD-MM-YY)*	2. REPORT TYPE	3. DATES COVERED *(From - To)*
August 2012	Technical Paper	1 July 2012 – 1 August 2012

4. TITLE AND SUBTITLE	5a. CONTRACT NUMBER
QUANTIFYING THE EFFECT OF 3D SPATIAL RESOLUTION ON THE ACCURACY OF MICROSTRUCTURAL DISTRIBUTIONS (PREPRINT)	In-house

	5b. GRANT NUMBER

	5c. PROGRAM ELEMENT NUMBER
	62102F

6. AUTHOR(S)	5d. PROJECT NUMBER
Michael D. Uchic and Michael Groeber (AFRL/RXCM)	4347
Megna Shah (UES, Inc.)	5e. TASK NUMBER
Gregory Loughnane, Raghavan Srinivasan, and Ramana Grandhi (Wright State University)	20
	5f. WORK UNIT NUMBER
Matthew Riley (University of Idaho)	X071

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)	8. PERFORMING ORGANIZATION REPORT NUMBER
Metals Branch (AFRL/RXCM) Structural Materials Division Air Force Research Laboratory, Materials and Manufacturing Directorate Wright-Patterson Air Force Base, OH 45433-7750 Air Force Materiel Command, United States Air Force	AFRL-RX-WP-TP-2012-0385

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)	10. SPONSORING/MONITORING AGENCY ACRONYM(S)
Air Force Research Laboratory Materials and Manufacturing Directorate Wright-Patterson Air Force Base, OH 45433-7750 Air Force Materiel Command United States Air Force	AFRL/RXCM
	11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S)
	AFRL-RX-WP-TP-2012-0385

12. DISTRIBUTION/AVAILABILITY STATEMENT
Approved for public release; distribution unlimited. Preprint to be submitted to International Conference on 3D Materials Science.

13. SUPPLEMENTARY NOTES
The U.S. Government is joint author of this work and has the right to use, modify, reproduce, release, perform, display, or disclose the work. PA Case Number and clearance date: 88ABW-2012-0673, 9 February 2012. This document contains color.

14. ABSTRACT
The choice of spatial resolution for experimentally-collected 3D microstructural data is often governed by general rules of thumb. For example, serial section experiments often strive to collect at least ten sections through the average feature-of-interest. However, the desire to collect high resolution data in 3D is greatly tempered by the exponential growth in collection times and data storage requirements. This paper explores the use of systematic down-sampling of synthetically-generated grain microstructures to examine the effect of resolution on the calculated distributions of microstructural descriptors such as grain size, number of nearest neighbors, aspect ratio, and the third moment invariant.

15. SUBJECT TERMS
microstructure, 3D characterization, serial sectioning, grain size

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT:	NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON (Monitor)
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified	SAR	12	Andrew Rosenberger 19b. TELEPHONE NUMBER (Include Area Code) N/A

Standard Form 298 (Rev. 8-98)
Prescribed by ANSI Std. Z39-18

Quantifying the effect of 3D spatial resolution on the accuracy of microstructural distributions

Gregory Loughnane[1], Michael Groeber[2], Michael Uchic[2], Matthew Riley[3], Megna Shah[4], Raghavan Srinivasan[1], and Ramana Grandhi[1]

[1] Wright State University, Department of Mechanical & Materials Engineering, Dayton, OH 45433
[2] Air Force Research Laboratory, Materials & Manufacturing Directorate, Wright-Patterson AFB, OH 45433
[3] University of Idaho, Moscow, ID 83844
[4] UES, Inc., Dayton, OH 45432

Abstract

The choice of spatial resolution for experimentally-collected 3D microstructural data is often governed by general rules of thumb. For example, serial section experiments often strive to collect at least ten sections through the average feature-of-interest. However, the desire to collect high resolution data in 3D is greatly tempered by the exponential growth in collection times and data storage requirements. This paper explores the use of systematic down-sampling of synthetically-generated grain microstructures to examine the effect of resolution on the calculated distributions of microstructural descriptors such as grain size, number of nearest neighbors, aspect ratio, and Ω_3.

Keywords

microstructure, 3D characterization, serial sectioning, grain size

Introduction

Three dimensional (3D) microstructure characterization techniques are required to measure many important microstructural characteristics including true size and shape, the number of features per volume, and feature connectivity [1]. Although the need for 3D characterization for 'complete' microstructural analysis is well known, it is only within the past decade that desktop computing resources—such as processor speed, memory, graphics cards, 64-bit operating systems—have advanced to the point where materials scientists and engineers are able to readily work with the enormous data sets born of 3D characterization experiments. These aforementioned advancements in computing technology have also helped galvanize activity in the materials community to promote and adopt Integrated Computational Materials Engineering (ICME) initiatives [2-4].

A foundational experimental technology for ICME-related research is the ability to quantify the internal material state at any point during the manufacturing or utilization of engineering materials, in order to verify and validate the output of modeling and simulation tools that examine such processes. This analysis ideally includes statistically-significant data on key microstructural features such as grains, precipitates, second phases, voids, and defects. Known capability gaps for this technology area include two topics related to 3D microstructure characterization; machines to rapidly collect 3D data across the range of lengths scales that are

1

known to affect material properties [5], and computational methods to streamline the process of data reduction, analysis, and further re-use of data by other modeling and simulation tools. With the advent of new state-of-the-art 3D characterization systems that are addressing the need for rapid data collection, it is important to examine and investigate the sources of error associated with these characterization processes, in order to bound the uncertainty in quantitative measurements derived from such experiments.

In particular, there is little information in the materials characterization literature to guide the selection of sampling resolution for data collection in 3D. Prior guidance is particularly important for destructive experiments such as serial sectioning, where the sample volume is incrementally and irreversibly consumed during the experiment. In the serial sectioning literature, it is generally espoused that one would like a minimum of ten sections through a microstructural feature to accurately describe its size and shape, but this guidance is simply a rule-of-thumb and is wholly insufficient for quantitative microstructural analysis. Experimentalists can always strive to refine the spatial frequency of data collection, but this becomes problematic for 3D data when the collection times and storage requirements grow exponentially, often leading to considerable inefficiencies due to conservative oversampling.

This paper examines one aspect of modeling uncertainty with regards to 3D data collection, which is the effect that isotropic decrements in spatial resolution have on the accuracy of microstructural distributions that are derived from a reference data volume. Specifically, this work reports the quantitative change in the full distribution for the following morphological microstructure parameters: grain size in equivalent sphere diameter (ESD), grain shape as described by the two ellipsoid ratios b/a and c/a, the third moment invariant Ω_3 [6], and the number of contiguous neighbors. This analysis is performed for two log-normal grain size distributions that have been synthetically-generated and virtually down-sampled, as described in the following section.

Methodology

The synthetic structure generation and subsequent data analysis for this study were performed using a state-of-the-art 3D materials analysis software DREAM.3D, or Digital Representation Environment for Analyzing Microstructure in 3D (dream3d.bluequartz.net). The 3D synthetic reference volumes were created using processes that are briefly described here; detailed reviews on synthetic microstructural generation methods have been reported previously [7].

The first step in the synthetic microstructure generation process is to define the grain size distribution and grain shape distribution for the desired volume. Two log-normal reference volumes were created, where each microstructural volume was composed of roughly equiaxed grains. One of the distributions was nearly uniform, which is termed 'slightly log-normal' ($\mu = 1.0$, $\sigma = 0.1$) while the other distribution had a much heavier tail ($\mu = 1.0$, $\sigma = 0.5$), in order to examine the effect that the grain size distribution on these uncertainty measurements of sampling frequency. After defining both size and ellipsoid aspect-ratio distributions (here the aspect ratio is defined to be unity for all grain sizes), a list of grains were generated to fill the reference volume via random sampling of these distributions. Voxelized grains were packed into the reference volume using a process termed grain seeding, which iteratively places the grains into the reference volume while optimizing a number of local descriptors and global

2

microstructural distributions (e.g., grain overlap, number of neighbors, orientation and misorientation distribution functions, etc…). After initial placement, a simulated annealing process was used to eliminate unassigned voxels within the reference volume. The two synthetic reference volumes are shown in Figure 1. Note that the reference volumes contain approximately 3000 grains, and a resolution of approximately 30 voxels spanning the mean grain size.

To quantify the effect of data resolution on the resultant microstructure parameter distributions, the two reference volumes were down-sampled using the following procedure. A new voxel volume was created using MATLAB at the desired down-sampling resolution. Grain IDs were assigned to voxels in the new volume by determining the reference volume voxel that coincided with the centroid location for each down-sampled voxel. Successively coarser re-samplings of the reference synthetic microstructure volume were produced in this manner (i.e., the reference volume was always used to assign the Grain ID), and the result of the down-sampling process is shown in Fig. 2.

The morphological characterization parameter distributions examined in this study include grain size (ESD), grain shape (b/a, c/a, Ω_3), and number of neighbors. The ESD is computed using the following relation, where N_v is the number of voxels that comprise the grain, V is the voxel volume:

$$ESD = 2 \cdot \left(\frac{3}{4\pi} N_V V \right)^{\frac{1}{3}} \tag{1}$$

Feature shape is described using moment invariants, or combinations of second order moments that are invariant with respect to affine and/or similarity transformations [6]. The length/width ellipsoid ratios *b/a* and *c/a* are essentially the first two moment invariants [7]. The third moment invariant, denoted by Ω_3, is used to further describe grain shape and is calculated using the following equation [6]:

$$\Omega_3 = \frac{V^5}{O_3} \tag{2}$$

$$O_3 = \mu_{200}\mu_{200}\mu_{200} + 2\mu_{110}\mu_{101}\mu_{011} - \mu_{200}\mu_{011}^2 - \mu_{020}\mu_{101}^2 - \mu_{002}\mu_{110}^2 \tag{3}$$

where μ_{pqr} represents the second order moments in Eq. 3 (moment order is equal to the sum of *p, q* and *r*). The third moment invariant Ω_3 can be used to differentiate shapes with the same aspect ratio, and shapes become qualitatively 'less complex' and more ellipsoidal-like with increasing values of Ω_3, up to the limiting case of $\Omega_3 = 2193.245$ that corresponds to spheres and ellipsoids [6].

The nearest neighbor distribution describes the number of grains that share at least one voxel face with a reference grain. Note that voxels which only share a common edge or corner are not considered as neighbor grains in this analysis.

3

The metric used to compare the change in the parameter distributions from reference volumes to those obtained via virtual down-sampling is the Bhattacharyya Coefficient (BC), which for discrete distributions is the following:

$$BC = \sum_{i=1}^{n} \sqrt{R_i}\,\sqrt{S_i} \qquad (4)$$

R_i and S_i correspond to the data percentage in bin i for the discrete distributions R and S. The BC is used to measure the geometric similarity between two distinct statistical distributions (models), and is bounded between 0 and 1, where a value of 1 implies that two models are identically distributed [8]. For this work, microstructure parameter data was binned into histograms after being computed from down-sampled and reference volumes. Therefore, the computation of the BC was done discretely using a direct comparison of histograms over the entire domain of possible parameter values [9].

Results and Discussion

A plot of the statistical analysis of the down-sampled volumes from the slightly log-normal grain size distribution is shown in Fig. 3. At 20 voxels spanning the mean grain size, the BC for all measured feature distributions are nearly equal to 1, which indicates that there is very little difference in the measured distributions. The shape parameter Ω_3 is the most sensitive to resolution changes and requires significantly more sections through each feature to retain a high BC. This sensitivity is highlighted by the decrease in the BC from 0.99 at 20 voxels spanning the mean grain size to a BC of 0.90 at 10 voxels. Importantly, the grain size, ellipsoid ratios b/a and c/a, and nearest neighbor distributions continue to match the reference volume distribuitons (BC > 0.98) with progressively-coarser down-sampling to as low as 5 voxels spanning the mean grain size. This resolution is considerably less than the traditional rule-of-thumb of 10 sections through the average feature. However, for sampling resolutions below 5, all of the feature distributions begin to deviate rapidly from the reference distribution, as the shape & volume for the smallest grains in the distribution are becoming strongly altered by the relative coarseness of the voxel array.

A plot of the statistical analysis of the down-sampled volumes from the heavy-tailed grain size distribution is shown in Fig. 4. The global trends in the data are similar to the slightly log-normal distribution: Ω_3 is the most sensitive to changes in sampling resolution (BC = 0.97 at 20 voxels spanning mean grain size), and save for this parameter, all other distributions had BC values greater than 0.97 at 5 voxels spanning the mean grain size. Note that the heavy-tailed volume contains comparatively more small grains relative to the slightly log-normal volume. As a result, the microstructural distributions calculated from the heavy-tailed volume are affected first by changes in resolution, given that the smallest grains will be most altered by sampling resolution changes (this holds only for resolutions ≥ 3 voxels per mean grain size).

This study highlights the intrinsic effect of sampling resolution on the accuracy of microstructural distributions derived from 3D data. The virtual down-sampling experiments show that the probability distributions for grain size, number of neighbors, and ellipsoid ratio can be collected at relatively coarse resolutions with little alteration. Conversely, selected

4

shape descriptors such as Ω_3 require high spatial resolution data. Although the methodology outlined herein has only been used to quantify one source of uncertainty, this method can be extended to examine many other sources data uncertainty, and will likely be especially effective with regards to improved analysis of destructive experimental methods like serial sectioning. For example, this approach could be used to optimize the selection of anisotropic sampling resolution (e.g., higher in-plane resolution relative to the sectioning depth), or examine the impact of variability within the serial sectioning process (planarity, parallelism, uniformity). While these concepts are not explored here and are left to future work, these types of studies should improve both data quality and experimental efficiencies.

References

[1]   DeHoff, R.T., J. Microsc. 131 (1983) 259–263.

[2]   Materials Genome Initiative for Global Competitiveness, June 2011

[3]   Allison, J., "Integrated Computational Materials Engineering: A Perspective on Progress and Future Steps," Journal of Materials, Vol. 63, No. 4, April, 2011, pp. 15-18.

[4]   Christodoulou, J., "Dynamic 3D Digital Structure: Program Overview," *Journal of Materials*, Vol. 61, No. 10, 2009, p. 21.

[5]   Uchic, M.D., Groeber, M.A., and Rollet, A.D., "Automated Serial Sectioning Methods for Rapid Collection of 3-D Microstructure Data," *Journal of Materials,* Vol. 63, No. 3, 2011, pp. 25-29.

[6]   MacSleyne, J.P., Simmons, J.P., and De Graef, M., "On the use of moment invariants for the automated analysis of 3D particle shapes," *Modelling and Simulation in Materials Science and Engineering*, Vol. 16, April, 2008,

[7]   Groeber, M.A., *Computational Methods for Microstructure-Property Relationships,* ed. Ghosh, S., and Dimiduk, D. (New York: Springer, 2011), pp. 53-97

[8]   Thacker N. A., Aherne, F. J. and Rockett, P. I. "The Bhattacharyya Metric as an Absolute Similarity Measure for Frequency Coded Data," *Kybernetika*, Vol. 34, No. 4, 1997, pp. 363-368.

[9]   Riley, M.E., and Grandhi, R.V., "Quantification of model form and predictive uncertainty for multi-physics simulation," *Computers and Structures*, Vol. 89, Issues 11-12, June 2011, pp.1206-1213.
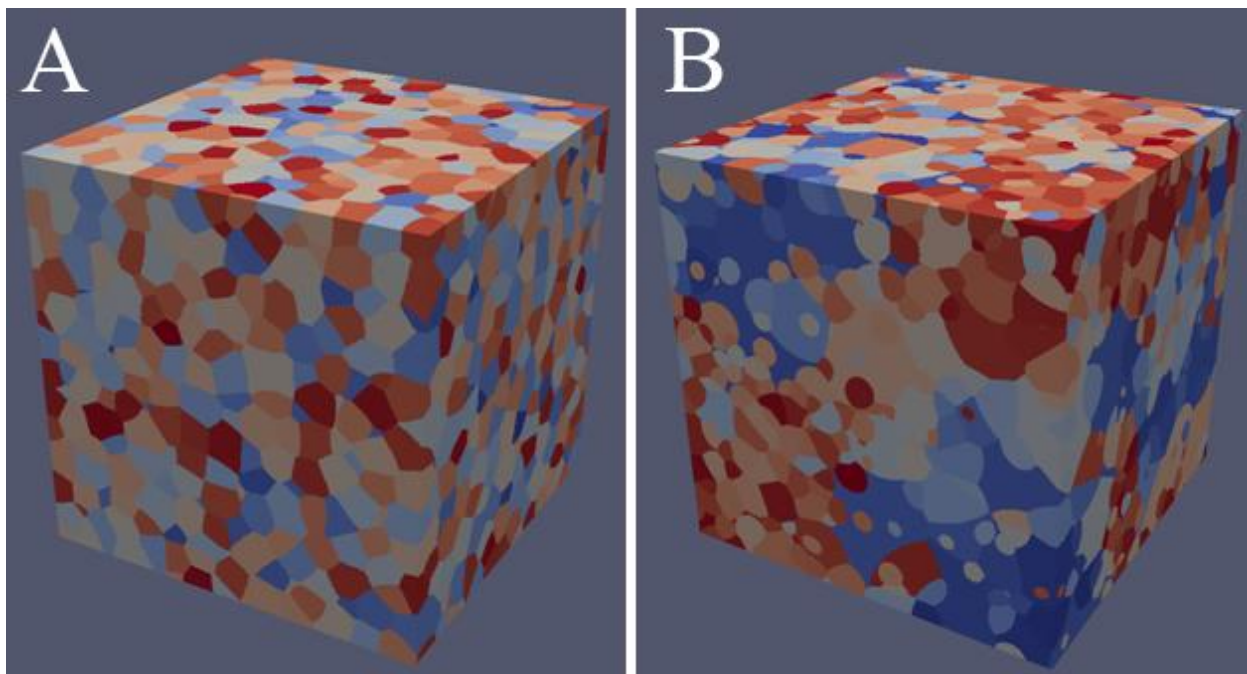
Figure 1: 3D renderings of the two synthetically-generated reference volumes. Panel A shows the slightly log-normal grain size distribution, while Panel B shows the heavier-tail grain size distribution. Grain coloring corresponds to unique grain IDs.
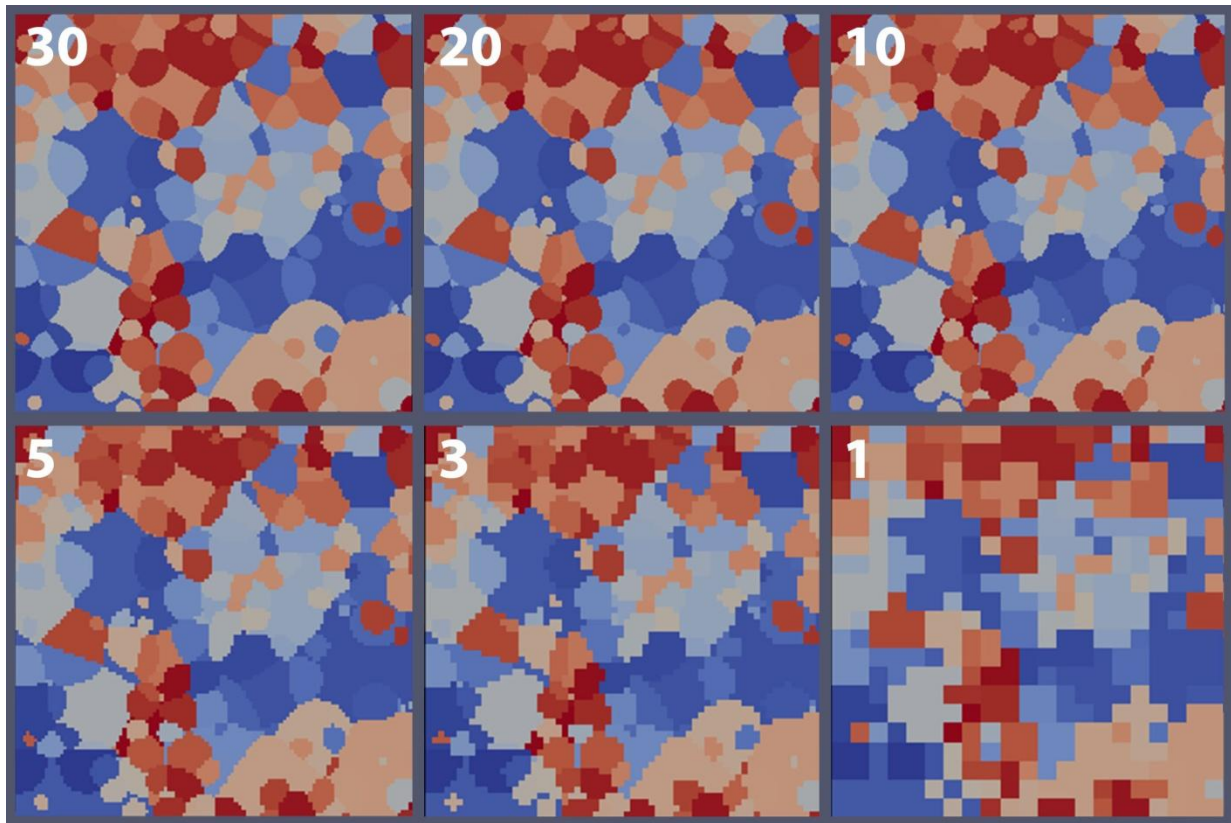
Figure 2: Images of successively down-sampled volumes for the heavy-tailed distribution. Spatial resolution is listed at the upper-left corner of each sub-image, which is defined as number of voxels that span the mean ESD.
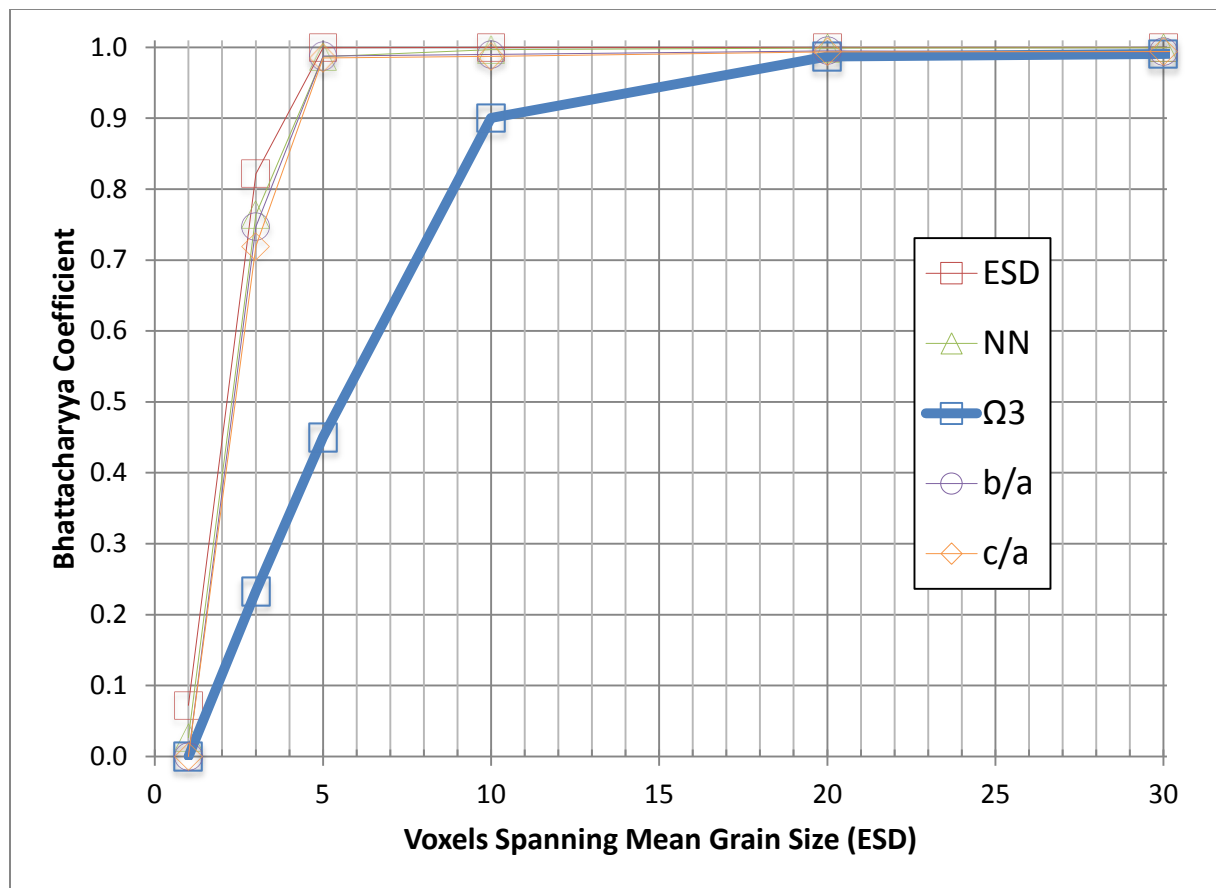
Figure 1: Plot of the Bhattacharyya Coefficient relative to the number of voxels that span the mean grain size for the slightly log-normal grain size distribution.
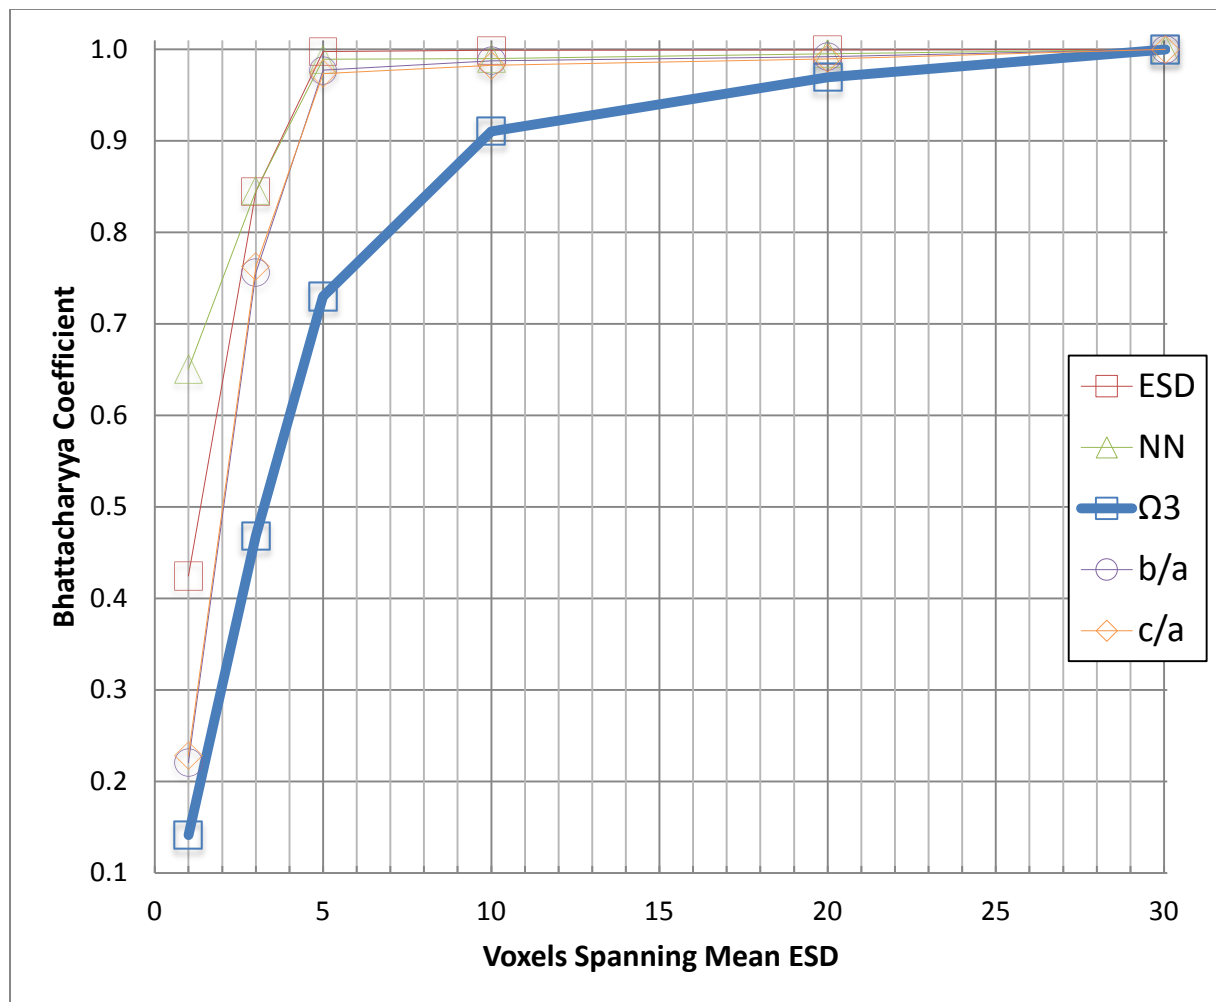
Figure 4: Plot of the Bhattacharyya Coefficient relative to the number of voxels that span the mean ESD for the heavier-tailed log-normal grain size distribution.